

Optical spectroscopy of trivalent chromium in sol-gel lithium niobate

J. K. Krebs

Dept. of Physics and Astronomy, Franklin and Marshall College, Lancaster, PA 17604

U. Happek

Dept. of Physics and Astronomy, The University of Georgia, Athens, GA 30602-2451

(Dated: February 2, 2008)

We report on the characterization of sol-gel derived lithium niobate via trivalent chromium probe ions, a study that is motivated by recent reports on the synthesis of high quality sol-gel lithium niobate (LiNbO_3). In order to assess the quality of sol-gel derived LiNbO_3 , we incorporate Cr^{3+} during the hydrolysis stage of the sol-gel process. A comparison of the Cr^{3+} emission and photoexcitation data on both sol-gel and melt-grown LiNbO_3 shows that the sol-gel derived material is highly stoichiometric.

PACS numbers: 78.55Hx, 71.55Ht, 71.70Ch, 77.84Bw

The need for sol-gel derived ferroelectric coatings and films for electro-optical and piezo-electric applications is driving the research for high quality sol-gel lithium niobate (LiNbO_3) [1, 2]. Recent reports concentrate on optimizing the sol-gel process with the aim of producing high quality films with preferred orientation. X-ray diffraction and ICP have been the primary techniques to assess stoichiometry of the samples. To our knowledge, optical probes, such as Cr^{3+} ions, have not been used to characterize the sol-gel samples, although this approach has been very successful to show fundamental differences between congruent and stoichiometric melt-grown LiNbO_3 [3]. The Cr^{3+} ion is particularly suited to study the quality of LiNbO_3 , because it is arguably the most studied optical impurity [4], has a spectrum that is very sensitive to the possible lattice sites and disorder in LiNbO_3 , and can be readily incorporated in an early stage of the sol-gel process. In addition, chromium doped lithium niobate has stimulated much interest due to the broadband near infrared luminescence of the chromium ions, with the ultimate goal of developing a tuneable laser in the visible range through frequency doubling within the active medium.

In the current work, we study the optical Cr^{3+} transitions between the 4A_2 groundstate and the lowest 4T_2 and 2E excited electronic states. These transitions are characterized by broad absorption and emission bands for the spin allowed transition, and spectrally narrow lines for the spin-forbidden transition, respectively. These transitions provide information on the stoichiometry and disorder of the sol-gel material, and allow a comparison to the detailed study of LiNbO_3 samples grown from melt.

For the sample synthesis, we combine 1 M solutions of lithium and niobium ethoxides in ethanol such that the ratio of Li:Nb is 1:1. An appropriate amount of $\text{Cr}(\text{NO}_3)_3$ is then dissolved in water (in this study the Cr:Li ratio was 0.001:1). Under constant stirring, the water-chromium solution is slowly added into the mixed ethoxide. After an initial release of ethanol, the solution is capped and aged for several days. The aged solution is then dried at room temperature until a fine white powder

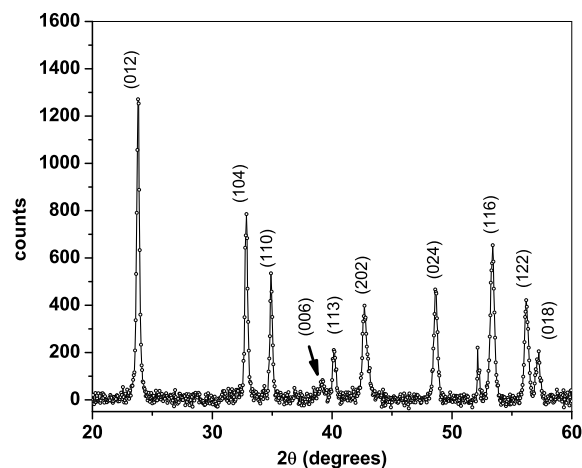


FIG. 1: X-ray diffraction pattern of sol-gel $\text{LiNbO}_3:0.1\%\text{Cr}^{3+}$.

has formed. The powder samples are finally heated in air to 800 °C for two hours to remove excess water and organic complexes. The calcined powders are characterized by x-ray diffraction utilizing Cu K-alpha radiation; a typical pattern is shown in Fig. 1. All observed diffraction peaks can be attributed to lithium niobate, and we find no evidence for alternate phases such as $\text{Li}_{0.88}\text{H}_{0.12}\text{NbO}_3$.

The optical experiments are carried out with the powder sample mounted in an Oxford Instruments temperature variable cryostat. For emission measurements the sample is excited with a HeNe laser at 632.8 nm. The broadband emission was collected with reflective optics and analyzed with a Bruker 66v FTIR spectrometer. Photoexcitation measurements were performed by mounting the cryostat directly into the sample space of a modified Cary 14 spectrophotometer. In both the broadband emission and photoexcitation experiments, the emitted light was collected through appropriate filters and imaged onto a liquid-nitrogen cooled InGaAs detector. For the photoexcitation, a lock-in amplifier was used

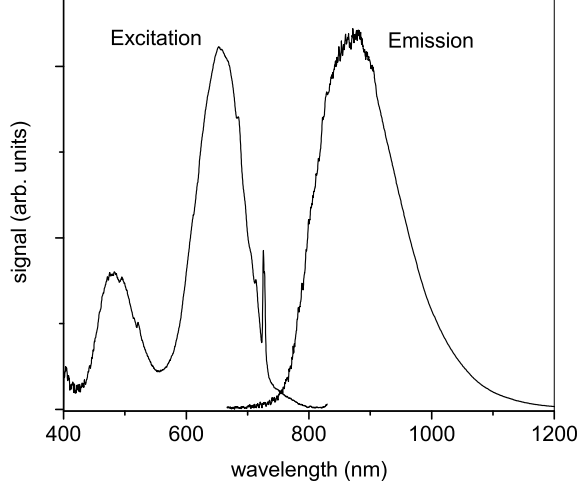


FIG. 2: Excitation and emission spectra from sol-gel $\text{LiNbO}_3:0.1\%\text{Cr}^{3+}$.

for signal-to-noise enhancement.

Experimental results for the sol-gel $\text{LiNbO}_3:0.1\%\text{Cr}^{3+}$ sample are shown in Fig. 2. The excitation spectrum (Fig. 2, left) observed at $\lambda_{\text{det}} \geq 900$ nm shows the characteristic ${}^4\text{A}_2 \rightarrow {}^4\text{T}_2$ and ${}^4\text{A}_2 \rightarrow {}^4\text{T}_1$ broad absorption bands around 655 nm and 480 nm, respectively, as well as the spin-forbidden ${}^4\text{A}_2 \rightarrow {}^2\text{E}$ transition around 726 nm. The emission spectrum (Fig. 2, right) shows the ${}^4\text{T}_2 \rightarrow {}^4\text{A}_2$ emission band under HeNe laser excitation ($\lambda_{\text{ex}} = 632.8$ nm).

To interpret these results, they are compared to spectra obtained on standard melt-grown $\text{LiNbO}_3:\text{Cr}^{3+}$. Lithium niobate crystals pulled from a melt with equal amounts of lithium and niobium crystallize with a Li 3% deficit [5], and are referred to as congruent samples. When chromium ions are added to these melts, the trivalent impurities preferentially occupy the crystallographic site of lithium vacancies, in the following referred to as Cr[Li]. The crystal field leads to strong absorption into the ${}^4\text{T}_2$ and ${}^4\text{T}_1$ levels peaking at 654 nm and 478 nm, respectively, giving the crystals a green color. A shift in the optical spectra is observed when $\text{LiNbO}_3:\text{Cr}^{3+}$ is codoped with more than 4.5% Mg^{2+} , resulting in Cr^{3+} impurities preferentially occupying niobium sites [6]. The resulting change in the crystal field shifts the ${}^4\text{T}_2$ and ${}^4\text{T}_1$ absorption peaks to 715 nm and 540 nm, resulting in a crystal with a red color. New crystal growth techniques, namely high-temperature top-seeded solution growth methods (HTTSSG), enabled the production of LiNbO_3 crystals that are stoichiometric (i.e. no Li or Nb deficit)[7]. These samples produce spectra with narrower linewidths enabling more precise optical spectroscopy and better characterization of the various chromium sites [3], moreover, the chromium ions in these stoichiometric melt-grown single crystals are found to oc-

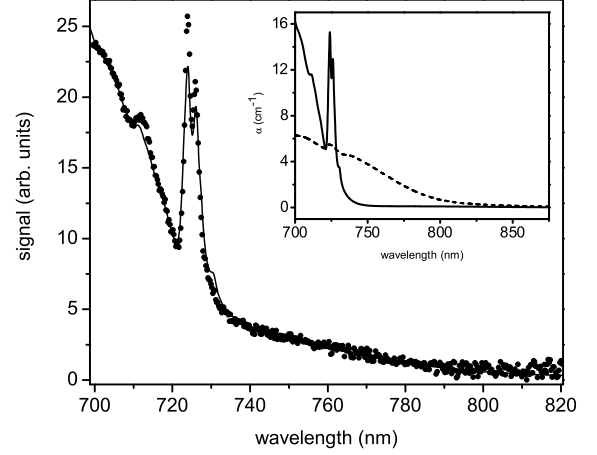


FIG. 3: Excitation of sol-gel $\text{LiNbO}_3:0.1\%\text{Cr}^{3+}$ (circles). The inset shows the absorption coefficient of Cr^{3+} ions in single crystal samples of LiNbO_3 and $\text{LiNbO}_3:6\%\text{Mg}$. The fit to the excitation spectrum determines the 66% Cr[Li] to 34% Cr[Nb] ratio.

cupy both Li and Nb sites [8].

In contrast to the Cr[Li] spectrum that dominates in congruent LiNbO_3 crystals, the sol-gel produced material has a significant contribution to the luminescence at excitation wavelengths beyond 750 nm, as evident in a shoulder in the excitation spectrum extending from about 750 nm to 800 nm in Fig. 2. Fig. 3 shows an expanded excitation spectrum in this region (dots). This shoulder can be attributed to chromium ions on niobium sites, Cr[Nb]. To quantify this contribution to the excitation spectrum, we measured the spectra of $\text{LiNbO}_3:\text{Cr}^{3+}$ crystals with and without magnesium codoping (6%).

The inset of Fig. 3 shows the absorption for the single crystal samples of $\text{LiNbO}_3:\text{Cr}$ (solid) and $\text{LiNbO}_3:\text{Cr:Mg}$ (dashed) in the 700 nm to 850 nm range, clearly demonstrating the difference of the ${}^4\text{T}_2$ onset for the two sites. The fit to the sol-gel data (Fig. 3, main plot, line) was found by varying the contributions to the impurity absorption for each site while keeping the total constant, i.e. $\alpha_{\text{sol-gel}} = C_{\text{Li}}\alpha_{\text{Cr[Li]}} + C_{\text{Nb}}\alpha_{\text{Cr[Nb]}}$, with $C_{\text{Li}} + C_{\text{Nb}} = 1$. The fit shown in Fig. 3 (solid line) represents a $C_{\text{Li}}=0.66$ contribution from the Cr[Li] and a $C_{\text{Nb}} = 0.34$ contribution from Cr[Nb]. This approach is justified because our single crystal reference samples contained the same amount of chromium ions (0.25%). A careful inspection of $\text{LiNbO}_3:\text{Cr:Mg}$ (insert Fig. 3, dashed line) shows a small peak at 727 nm (${}^4\text{A}_2 \rightarrow {}^2\text{E}$ transition), due to Cr[Li]. Taking this correction into account, we arrive at relative Cr[Li] and Cr[Nb] concentrations of 0.64 and 0.36, respectively.

The substantial occupation of the niobium site by chromium ions is in marked difference to melt-grown congruent samples, where the chromium ions occupy lithium

sites exclusively. In highly stoichiometric LiNbO_3 samples, grown by the HTTSSG method [7], we also find chromium ions on both the lithium and niobium sites [8], thus our results confirm reports that the sol-gel process yields highly stoichiometric samples without the intrinsic Li deficit, which is characteristic for congruent melt-grown LiNbO_3 . In stoichiometric single crystal samples of highest quality, the zero-phonon line of the ${}^4\text{A}_2 \rightarrow {}^4\text{T}_2$ can be observed at low temperature. In our sample, this transition is broadened, which is indicative of lattice defects. Our sample also shows the optical signature of so-called high field sites, which is due to Cr^{3+} ions in a strong crystal field, resulting in the ${}^2\text{E}$ level lying below the ${}^4\text{T}_2$ level, characterized by sharp emission lines at low temperatures, and which are associated with defects in the crystal. Thus, while our results indicate that the sol-gel samples do not have the intrinsic lithium deficit of

congruent melt-grown material, the overall quality of the material does not yet approach that of the highest quality single crystal material. However, with the optical absorption and emission spectra of trivalent chromium being a clear indicator of the crystal quality, systematic studies are possible to improve the quality of sol-gel derived LiNbO_3 .

In summary, we have shown Cr^{3+} ions are sensitive optical probes of the quality of sol-gel derived LiNbO_3 . Our experiments confirm that sol-gel produced lithium niobate is highly stoichiometric and does not contain the intrinsic Li deficit of congruent LiNbO_3 . Our results also show that our sol-gel material contains more defects than high quality stoichiometric LiNbO_3 . With the aid of the chromium optical probe ions, experiments are under way to improve the quality of sol-gel LiNbO_3 and related ferroelectric materials.

-
- [1] Shin-ichi Hirano, Y. Takeichi, W. Sakamoto, and T. Yogo, *Journal of Crystal Growth* **237-239**, 2091 (2002).
 - [2] S. Cheng, X. Han, C. Kam, Y. Zhou, Y. Lam, J. T. Oh, X. Xu, and T. Chong, *Applied Physics A* **73**, 511 (2001).
 - [3] G. Salley, S. Basun, A. Kaplyanskii, R. Meltzer, K. Polgar, and U. Happek, *Journal of Luminescence* **87-89**, 1133 (2000).
 - [4] B. Henderson and G. Imbusch, *Optical Spectroscopy of Inorganic Solids* (Oxford University Press, Clarendon, Oxford, 1989).
 - [5] R. Byer, J. Young, and R. Feigelson, *Journal of Applied Physics* **41**, 2320 (1970).
 - [6] P. I. Macfarlane, K. Holliday, J. F. Nicholls, and B. Henderson, *Journal of Physics: Condensed Matter* **7**, 9643 (1995).
 - [7] K. Polgar, A. Peter, L. Kovacs, G. Corradi, and Z. Szaller, *Journal of Crystal Growth* **177**, 211 (1997).
 - [8] G. Salley, Ph.D. thesis, The University of Georgia (2000).